

NEW CATHODE MATERIALS FOR ITSOFC : THE $\text{Ln}_{2-x}\text{NiO}_{4+\delta}$ NICKELATES

J-C. Grenier, J-M. Bassat, E. Boehm,
P. Dordor, F. Mauvy, H. Zhao and Ph. Stevens*
ICMCB-CNRS, Institut de Chimie de la Matière
Condensée de Bordeaux , 87 Av. du Dr Schweitzer,
33 608 PESSAC Cedex (France)
* Forschungszentrum Umwelt, European Institut for
Energy Research (EDF Institut)
Universität Karlsruhe, 76128 Karlsruhe, Germany
GDR ITSOFC 700 - CNRS

Decreasing the operating temperature of SOFC down to 700 °C requires to find new materials for electrolytes as well as for electrodes. MIEC (mixed ionic electronic conducting) oxides are of great interest for that purpose ; we investigated a new family of compounds exhibiting enhanced performances as cathodes.

We report the preparation and characterization of these oxides formulated $\text{Ln}_{2-x}\text{NiO}_{4+\delta}$, $\text{Ln} = \text{La}, \text{Pr}, \text{Nd}$. From a structural point of view, they correspond to the $n = 1$ member of the Ruddlesden-Popper series and crystallize with the K_2NiF_4 - type structure. The main feature of these oxides is the presence of additional oxygen atoms located in interstitial sites of the Ln_2O_2 layers of the structure (Fig. 1). The value of the oxygen excess δ depends on the nature of the A cation and on the temperature. It has been determined by both chemical and thermal-gravimetry analyses. A decrease of the oxygen content is observed with increasing temperature but this does not affect significantly their dilatometric properties. The thermal expansion coefficient (TEC) of these materials is about 13.10^{-6}K^{-1} and is consistent with the values of the usual SOFC electrolytes ($\text{TEC} \approx 10\text{-}12.10^{-6}\text{K}^{-1}$ for zirconia and ceria).

Due to the presence of the mixed valency $\text{Ni}^{2+} / \text{Ni}^{3+}$, these compounds show a high electronic conductivity (about $10^1\text{-}10^2\text{ S.cm}^{-1}$ at 700°C), which meets the requirements for SOFC cathode materials. The oxygen diffusion properties have been studied using ^{18}O doping and SIMS (Secondary Ion Mass Spectroscopy) measurements. The oxygen diffusion coefficient D^* as well as the surface exchange coefficient k have been determined at various temperatures. The D^* and k coefficients of these nickelates as well as the oxygen ionic conductivity are, at 700°C, one order of magnitude higher than those of the best perovskite-type materials which are currently used (Fig. 2).

Electrochemical measurements have been carried out using impedance spectroscopy in order to determine the polarization resistance R_p (or the ASR in $\Omega.\text{cm}^2$) of porous cathodes at various overpotentials (Fig. 3). The various contributions included in the polarization resistance, *e.g.* oxygen adsorption and dissociation on the cathode surface, oxygen diffusion in the cathode material, charge transfer between the cathode and the electrolyte are discussed.

Preliminary experiments concerned with the reactivity of these nickelates with zirconia and ceria have also been achieved. Some compositions show a good stability as a function of time.

These results show that these nickelates exhibit promising diffusion and electrocatalytic properties and especially in comparison with the performances of the best perovskite materials as $\text{La}_{0.6}\text{Sr}_{0.4}\text{Fe}_{0.8}\text{Co}_{0.2}\text{O}_{3-\delta}$ (LSFC). This is discussed in terms of the 2D structural features of these materials.

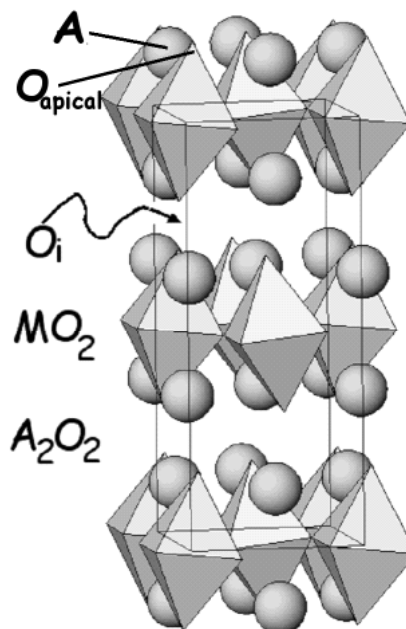


Fig. 1 Structure of $\text{Ln}_2\text{NiO}_{4+\delta}$ materials : additional oxygen atoms are inserted into the Ln_2O_2 layer.

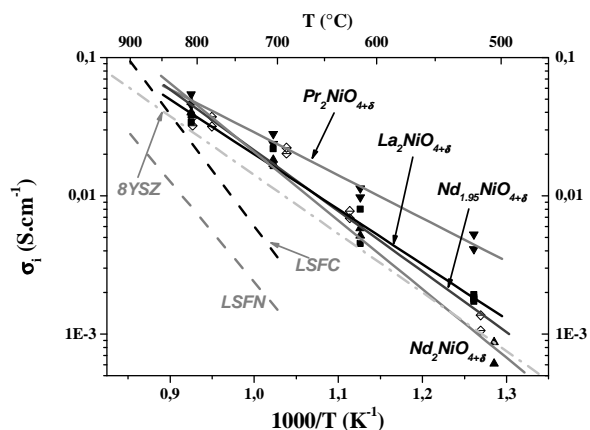


Fig. 2 Thermal evolution of the ionic conductivity of some $\text{Ln}_2\text{NiO}_{4+\delta}$ cathode materials compared with those of the perovskites and of stabilized zirconia.

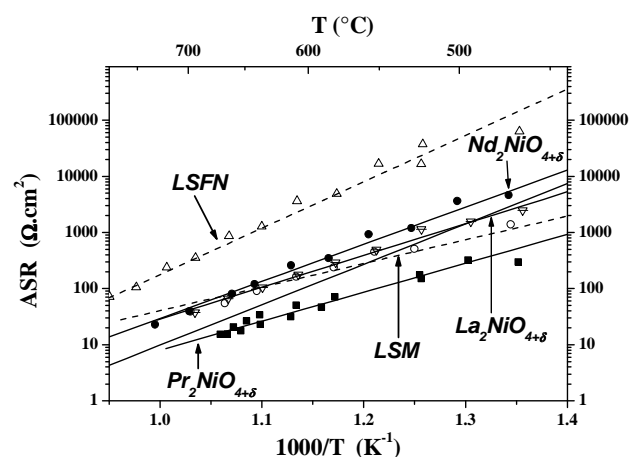


Fig. 3 Thermal evolution of the ASR of $\text{Ln}_2\text{NiO}_{4+\delta}$ / 8YSZ half-cells .

